

Polymer Glass-Formation in Variable Dimension*

Wen-Sheng Xu,^{1,†} Jack F. Douglas,^{2,‡} and Karl F. Freed^{1,3,§}

¹*James Franck Institute, The University of Chicago, Chicago, Illinois 60637, USA*

²*Materials Science and Engineering Division, National Institute of Standards and Technology, Gaithersburg, Maryland 20899, USA*

³*Department of Chemistry, The University of Chicago, Chicago, Illinois 60637, USA*

(Dated: November 9, 2016)

We explore the nature of glass-formation in variable spatial dimensionality (d) based on the generalized entropy theory, a synthesis of the Adam-Gibbs model with direct computation of the configurational entropy of polymer fluids using an established statistical mechanical model. We find that structural relaxation in the fluid state asymptotically becomes Arrhenius in the $d \rightarrow \infty$ limit and that the fluid transforms upon sufficient cooling above a critical dimension near $d = 8$ into a dense amorphous state with a finite positive residual configurational entropy. Direct computations of the isothermal compressibility and thermal expansion coefficient, taken to be physical measures of packing frustration, demonstrate that these fluid properties strongly correlate with the fragility of glass-formation.

PACS numbers: 64.70.Q-

Growing evidence indicates that molecular packing plays an essential role in both the physics of crystallization [1–5] and glass-formation [6–17], prompting a consideration of variable spatial dimensionality (d) as a conceptual probe of these solidification processes. In particular, the “decorrelation principle”, recently proposed by Torquato and Stillinger [18, 19], states that unconstrained correlations in hard hyperspheres diminish with increasing d and vanish in the $d \rightarrow \infty$ limit. Likewise, recent simulations [7–9] have indicated that certain often cited aspects of glass-formation, such as the dynamic heterogeneity and the decoupling between structural relaxation and diffusion, become diminished at elevated d . While prior studies [11–15] have focused mainly on how critical packing fractions associated with glass-formation in hard hyperspheres vary with d , little is known concerning the d dependence of the characteristic temperatures and fragility of glass-formation in molecular fluids. No prior work has considered complex fluids, such as polymeric liquids, where many molecular parameters may be tuned to control the nature of glass-formation.

In this Letter, we consider the glass-formation of a model polymer glass-forming (GF) liquid in d dimensions. Our approach is based on the generalized entropy theory (GET) [20], which is a combination of the lattice cluster theory (LCT) [21] and the Adam-Gibbs (AG) theory [22] linking the configurational entropy s_c (i.e., the entropy devoid of the vibrational component) to the structural relaxation time τ_α . The LCT employs a d -dimensional hypercubic lattice model, whose use facilitates the development of an expansion about the mean-field limit of infinite d . The LCT thus naturally provides

a framework for considering the d dependence of polymer thermodynamic properties, thereby making the GET suitable for exploring glass-formation in d dimensions.

As a primary result, we find that structural relaxation in the fluid state asymptotically becomes Arrhenius in the $d \rightarrow \infty$ limit [23], a limiting behavior that is a dynamical counterpart of the decorrelation principle of Torquato and Stillinger [18, 19]. Moreover, our theory indicates that the fluid transforms upon cooling above a critical dimension near $d = 8$ into a dense amorphous state with a finite positive residual configurational entropy. We show that the “kinetic fragility”, determined from the temperature (T) dependence of τ_α , decreases with d , while the “thermodynamic fragility”, defined as the relative rate of change of s_c with respect to T , increases with d , in accord with recent simulations for soft-sphere liquids for $d = 2, 3$, and 4 [7]. Analyses of the isothermal compressibility and thermal expansion coefficient, taken to be physical metrics of packing frustration, indicate that molecular packing becomes more efficient in higher d , and, as anticipated, these thermodynamic properties strongly correlate with the d dependence of the fragility. We thus confirm the qualitative *geometrical* origin of the reduced kinetic fragility upon increasing d .

We consider a d -dimensional melt of chains with the structure of polypropylene (PP) [20]. For comparative purposes, a common parameter set is used in all d : the microscopic cohesive energy is $\epsilon = 200$ K, the bending energy is $E_b = 800$ K, and the polymerization index is $N_c = 8000$. By employing these parameters, the GET calculations for constant pressure ($P = 0$ MPa) polymer melts for $d = 3$ yield the glass transition temperature T_g and fragility [24] which are typical of synthetic GF polymers.

The temperature dependence of the configurational entropy is central to the AG model. Hence, we first focus on this quantity in d dimensions. The GET considers the configurational entropy density s_c (i.e., the configu-

* Contribution of the National Institute of Standards and Technology - Work not subject to copyright in the United States.

† wsxu@uchicago.edu

‡ jack.douglas@nist.gov

§ freed@uchicago.edu

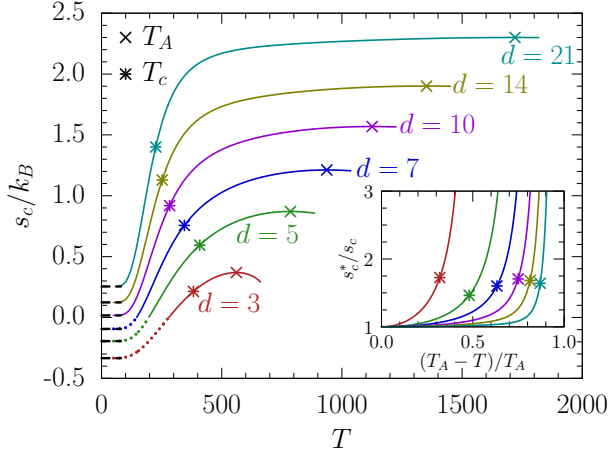


FIG. 1. Main: s_c/k_B as a function of T for various d at $P = 0$ MPa. Dotted lines highlight where s_c is negative, an unphysical behavior that is probably an artifact of high T expansion in the LCT for low d and a mathematical feature that disappears for higher d . Dashed lines denote the low T constants of s_c/k_B for each d . Inset: s_c^*/s_c as a function of $(T_A - T)/T_A$ for various d .

rational entropy per lattice site [20]) at constant P ,

$$P = - \left. \frac{\partial F}{\partial V} \right|_{N_p, T} = - \frac{1}{V_{\text{cell}}} \left. \frac{\partial F}{\partial N_l} \right|_{N_p, T}, \quad (1)$$

where F is the Helmholtz free energy [21], $V = N_l V_{\text{cell}}$ is the total volume of the system with N_l and V_{cell} the number of total lattice sites and the volume associated with a single lattice site, and N_p is the number of polymer chains. While V_{cell} in d dimensions may be defined in terms of the volume $V_{\text{cell}} = a_{\text{cell}}^d$ of a d -dimensional cube with a_{cell} the edge length, basic quantities, such as Boltzmann's constant k_B , cannot be determined in $d > 3$. We surmount this problem by performing all calculations at $P = 0$ MPa in all d since this condition completely eliminates problems in estimating V_{cell} and k_B in $d > 3$.

Figure 1 displays the calculated s_c/k_B as a function of T for various d . As in $d = 3$, s_c for larger d displays a shallow maximum s_c^* (crosses in Fig. 1) at a high T that defines the onset temperature T_A of glass-formation in the GET that signals the onset of non-Arrhenius behavior of τ_α [20], and the product $s_c T$ exhibits an inflection point (asterisks in Fig. 1) at a lower T that uniquely defines the crossover temperature T_c in the GET that separates two regimes of T with qualitatively different dependences of τ_α on T [20]. Evidently, s_c formally becomes negative (dotted lines in Fig. 1) at low T and low d in our mean-field theory, an unphysical behavior that is probably an artifact of high T expansion implicit to the LCT [25]. However, taken at face value, the point at which s_c vanishes signals a divergence of τ_α in the AG model. The existence of an equilibrium solidification transition in a disordered material implies that the transition must have the mathematical character of

a second-order phase transition, exactly the interpretation made long ago for the glass transition by Gibbs and DiMarzio [26].

The GET generally predicts the presence of a low T plateau in s_c (denoted by $s_{c,r}$; see the dashed lines in Fig. 1). This plateau increases linearly with $\ln(d/2)$ and becomes *positive* beyond a critical dimension d_c [27], and hence, an “ideal glass transition temperature” T_0 , where s_c formally vanishes, only exists for $d < d_c$ in the GET. We further find that d_c is independent of ϵ and E_b but varies with N_c for a fixed molecular structure and that d_c is near $d = 8$ for the PP structure [27]. Some recent models of glass-formation [16, 17] predict a critical dimension of $d_c = 8$ above which the Stokes-Einstein relation holds, a prediction that might be related to the behavior displayed in Fig. 1.

The evidence for a nonzero residual entropy in the glassy state has been a matter of long-standing discussion [28]. According to the AG theory, the appearance of a positive constant s_c implies that τ_α does not diverge at $T > 0$ K and that structural relaxation becomes Arrhenius again at low T , albeit with a much higher activation free energy than that above T_A . The ratio of the Arrhenius activation free energies in the low and high T Arrhenius regimes above d_c can be calculated as $s_c^*/s_{c,r}$, a quantity that is evidently larger than unity and that decreases with d as $s_c^*/s_{c,r} = 1/[A - B/\ln(d/2)]$ with the fitted constants, $A = 0.325$ and $B = 0.505$ [27]. Since τ_α becomes astronomically large in the low T Arrhenius regime, the thermodynamic state in this regime can be considered to be a “glass”. Notably, s_c appears to exhibit a step drop towards $s_{c,r}$ near T_c for large d , suggesting that the fluid transforms into a glass at a finite T upon cooling through a first-order phase transition in the $d \rightarrow \infty$ limit. Interestingly, the “tiling model” of glass-formation, developed by Weber and Stillinger [29, 30], predicts the glass transition to be first-order.

We now consider the T dependence of τ_α in d dimensions, which is obtained in the GET through the AG relation [22],

$$\tau_\alpha = \tau_\infty \exp[\varepsilon_{\text{AG}}/(k_B T)], \quad \varepsilon_{\text{AG}} = \Delta\mu(s_c^*/s_c), \quad (2)$$

where τ_∞ is the high T limit of τ_α , ε_{AG} is the AG activation free energy, and $\Delta\mu$ is the T independent activation free energy at high T above T_A where the Arrhenius dependence of τ_α holds. τ_∞ in $d = 3$ is taken in the GET as a “default” value of 10^{-13} s. Since τ_∞ is expected to be non-universal in variable d , we consider only the dimensionless relaxation time $\tau_r = \tau_\alpha/\tau_\infty$. The GET estimates $\Delta\mu$ in $d = 3$ from the empirical relation, $\Delta\mu/k_B = 6 T_c$ [20]. Simulations for $d = 2, 3$, and 4 [7, 31] suggest that $\Delta\mu$ increases approximately in proportion to d . This phenomenology is quite understandable from classical arguments by Eyring [32] relating $\Delta\mu$ to the cohesive interaction strength of the fluid, which scales in a hypercubic lattice model in proportion to the coordination number ($2d$). The scaling of $\Delta\mu$ with $2d$ implies that $\Delta\mu$ in the GET obeys $\Delta\mu/k_B = 2d T_{c,d=3}$, where

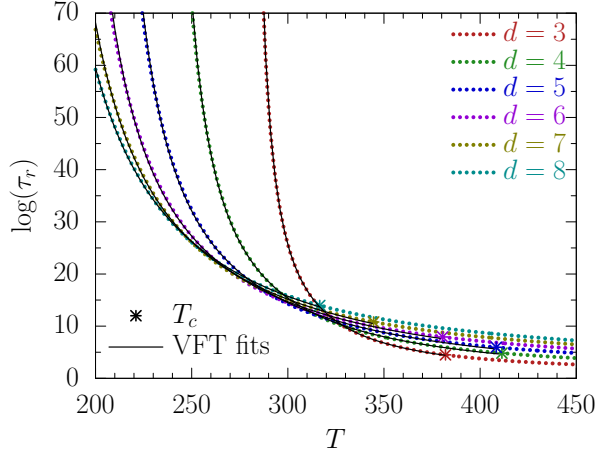


FIG. 2. $\log(\tau_r)$ as a function of T for various d .

$T_{c,d=3}$ is the T_c in $d = 3$.

Before analyzing the T dependence of τ_r , we investigate the T dependence of s_c^*/s_c in d dimensions, which describes the multiplicative increase of ε_{AG} . The inset to Fig. 1 displays s_c^*/s_c for various d as a function of $(T_A - T)/T_A$, a reduced temperature that measures the degree of quench into the “congested” regime of glassy dynamics. The growth of ε_{AG} with increasing d and, correspondingly with the scale of collective motion, weakens for fixed $(T_A - T)/T_A$. Evidently, the GET predicts that structural relaxation in the fluid state becomes Arrhenius in the $d \rightarrow \infty$ limit where s_c^*/s_c approaches unity asymptotically. Previous work [20] indicates that s_c^*/s_c for $d = 3$ exhibits a parabolic dependence on $(T_A - T)/T_A$,

$$s_c^*/s_c = 1 + C_s[(T_A - T)/T_A]^2, \quad T_c < T < T_A. \quad (3)$$

C_s measures the extent of cooperative motion at high T in the GET [20], and we find that Eq. (3) holds well in $(T_A - 50, T_A)$ in $d \geq 3$.

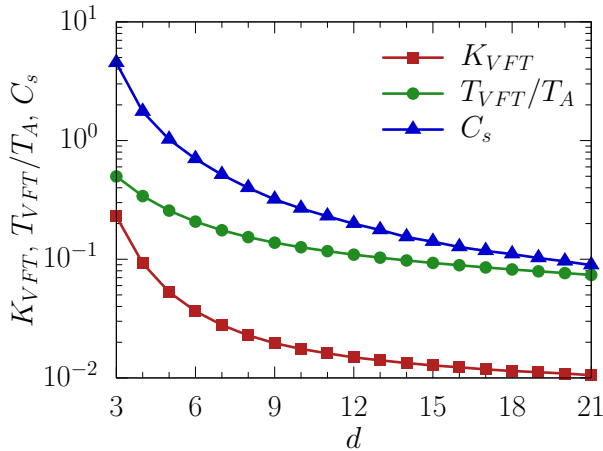


FIG. 3. K_{VFT} , T_{VFT}/T_A , and C_s as a function of d .

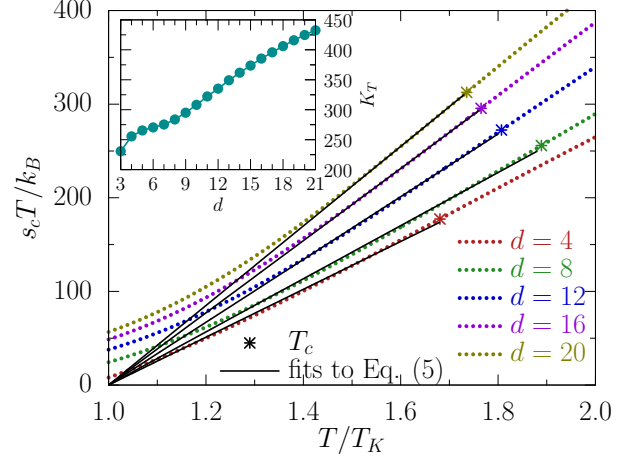


FIG. 4. Main: $s_c T/k_B$ as a function of T/T_K for various d . Inset: K_T as a function of d .

Figure 2 displays the T dependence of $\log(\tau_r)$ for various d , along with the fits to the Vogel-Fulcher-Tammann (VFT) equation,

$$\tau_r = \tau_0 \exp \left[\frac{1}{K_{VFT}(T/T_{VFT} - 1)} \right], \quad (4)$$

where τ_0 , K_{VFT} , and T_{VFT} designate the high T limit of τ_r , the “kinetic fragility” parameter quantifying the degree to which relaxation is non-Arrhenius, and the VFT temperature where τ_r extrapolates to infinity, respectively. Previous analyses for $d = 3$ [20] have shown that the VFT equation describes τ_α calculated from the GET quite well within the T range between T_c and T_g . Since we are unable to define T_g in $d > 3$ in terms of a characteristic timescale, VFT fits are performed for the T range between T_c and a lower temperature T_l at which $\log[\tau_r(T_l)] = 63$ [33]. The d dependence of K_{VFT} is depicted in Fig. 3, along with C_s and the ratio T_{VFT}/T_A , a measure of the “breadth” of glass-formation [20]. All these three metrics for glassy dynamics *decrease* with d .

Following the simulation studies [7], we additionally explore how d alters the “thermodynamic fragility” parameter K_T , determined from the slope of the T dependence of the product $s_c T$,

$$s_c T/k_B = K_T(T/T_K - 1), \quad (5)$$

where T_K is the Kauzmann temperature, estimated by linearly extrapolating $s_c T$ to zero over the same T range where K_{VFT} is obtained (see Fig. 4). We prefer to call K_T the “low T thermodynamic steepness” parameter because this parameter bears no direct relation to the strength of the T dependence of τ_α . The inset to Fig. 4 indicates that K_T *increases* with d , in agreement with the trend found in recent simulations of soft-sphere GF liquids in $d = 2, 3$, and 4 [7]. Reference [7] also shows, based on limited data from simulations, that K_{VFT} seems to weakly increase with d in the same model [34].

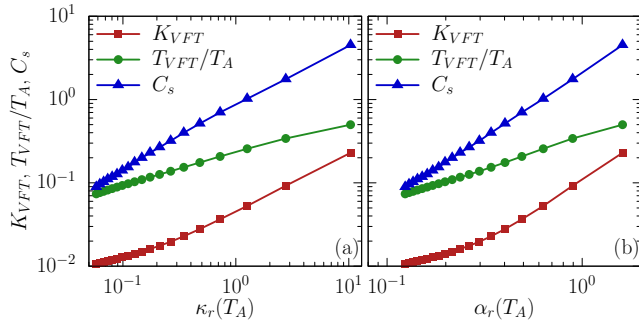


FIG. 5. Correlations between K_{VFT} , T_{VFT}/T_A , C_s and (a) $\kappa_r(T_A)$ and (b) $\alpha_r(T_A)$.

Our theory, thus, predicts that K_{VFT} varies in the *opposite* direction as K_T when d grows. An opposite dependence of K_{VFT} and K_T is also found in 3-dimensional simulations of GF liquids in which particles interact with a modified Lennard-Jones potential [35], where the potential softness is tuned to alter the fragility and where the inverted variations of K_T and K_{VFT} have been attributed to variations in $\Delta\mu$. Apparently, the same mechanism also explains our results since $\Delta\mu$ scales with $2d$ so that $\Delta\mu$ can be the dominant contribution to K_{VFT} for high d .

We now seek what physical factors govern the fragility of glass-formation. Building on the earlier GET calculations for $d = 3$ indicating that the fragility of polymer GF liquids primarily arises from packing frustration [20], we explore physical metrics that might best describe packing frustration. We consider the isothermal compressibility $\kappa_T = -(1/V) (\partial V/\partial P)|_T$ and the thermal expansion coefficient $\alpha_P = (1/V) (\partial V/\partial T)|_P$ as possible physical measures of packing frustration. In particular, we analyze $\kappa_r = \kappa_T(k_B T)/\rho$ (where $\rho = \varphi V_{\text{cell}}$ with φ the polymer filling fraction [21]) and $\alpha_r = T\alpha_P$, since these reduced quantities are found to strongly correlate with fragility in $d = 3$. (A more detailed discussion for $d = 3$ will be presented elsewhere.) As expected, as d grows, the T dependence of κ_r and α_r weakens and their overall magnitudes greatly decreases, thereby re-

flecting the diminished packing frustration with increasing d [27]. As an illustration, Fig. 5 exhibits the presence of strong correlations between various dynamic metrics (K_{VFT} , T_{VFT}/T_A , and C_s) and $\kappa_r(T_A)$ and $\alpha_r(T_A)$, implying that the d dependence of fragility can be predicted from a knowledge of the physical measures of packing frustration. Therefore, both the reduced fragility with increasing d and the corresponding return to Arrhenius relaxation are consequences of the reduction of packing frustration in higher d where space is more “open” and packing constraints are more weakly “felt”.

In summary, our exploration of polymer glass-formation in variable dimension indicates some clear trends as the dimensionality is varied. Perhaps most basically, we find that structural relaxation in the fluid state asymptotically becomes Arrhenius in the $d \rightarrow \infty$ limit and that the fluid transforms upon cooling above a critical dimension near $d = 8$ into an amorphous state with a finite positive residual configurational entropy. The transition from a fragile glass-forming liquid in low dimensions to an ideally strong liquid in the $d \rightarrow \infty$ limit indicates that the kinetic fragility decreases with increasing dimension. In accord with simulations [7], our theory predicts that the thermodynamic fragility K_T grows at elevated d . K_T fails to be a fragility parameter, and we suggest that K_T be termed the “low temperature thermodynamic steepness” parameter. By establishing strong correlations between the isothermal compressibility and thermal expansion coefficient and the fragility, we suggest that these thermodynamic properties should provide physical metrics of packing frustration for predicting fragility variations in glass-forming liquids.

ACKNOWLEDGMENTS

We thank Jacek Dudowicz for his numerous contributions to the development of the entropy theory of glass-formation that have helped make the present work possible. This work is supported by the U.S. Department of Energy, Office of Basic Energy Sciences, Division of Materials Sciences and Engineering under Award de-sc0008631.

-
- [1] B. Bagchi and S. A. Rice, J. Chem. Phys. **88**, 1177 (1988).
 - [2] S. Torquato, J. Chem. Phys. **136**, 054106 (2012).
 - [3] S. Torquato and Y. Jiao, J. Chem. Phys. **137**, 074106 (2012).
 - [4] R. Finken, M. Schmidt, and H. Löwen, Phys. Rev. E **65**, 016108 (2001).
 - [5] J. A. van Meel, B. Charbonneau, A. Fortini, and P. Charbonneau, Phys. Rev. E **80**, 061110 (2009).
 - [6] M. Skoge, A. Donev, F. H. Stillinger, and S. Torquato, Phys. Rev. E **74**, 041127 (2006).
 - [7] S. Sengupta, S. Karmakar, C. Dasgupta, and S. Sastry, J. Chem. Phys. **138**, 12A548 (2013).
 - [8] J. D. Eaves and D. R. Reichman, Proc. Natl. Acad. Sci. U.S.A. **106**, 15171 (2009).
 - [9] B. Charbonneau, P. Charbonneau, Y. Jin, G. Parisi, and F. Zamponi, J. Chem. Phys. **139**, 164502 (2013).
 - [10] S. Sengupta, S. Karmakar, C. Dasgupta, and S. Sastry, Phys. Rev. Lett. **109**, 095705 (2012).
 - [11] P. Charbonneau, A. Ikeda, G. Parisi, and F. Zamponi, Phys. Rev. Lett. **107**, 185702 (2011).
 - [12] G. Parisi and F. Zamponi, Rev. Mod. Phys. **82**, 789 (2010).
 - [13] A. Ikeda and K. Miyazaki, Phys. Rev. Lett. **104**, 255704 (2010).

- [14] B. Schmid and R. Schilling, Phys. Rev. E **81**, 041502 (2010).
- [15] Y. Jin, P. Charbonneau, S. Meyer, C. Song, and F. Zamponi, Phys. Rev. E **82**, 051126 (2010).
- [16] G. Biroli and J.-P. Bouchaud, J. Phys.: Condens. Matter **19**, 205101 (2007).
- [17] S. Franz, G. Parisi, F. Ricci-Tersenghi, and T. Rizzo, Eur. Phys. J. E **34**, 102 (2011).
- [18] S. Torquato and F. H. Stillinger, Phys. Rev. E **73**, 031106 (2006).
- [19] S. Torquato, O. U. Uche, and F. H. Stillinger, Phys. Rev. E **74**, 061308 (2006).
- [20] J. Dudowicz, K. F. Freed, and J. F. Douglas, Adv. Chem. Phys. **137**, 125 (2008).
- [21] K. W. Foreman and K. F. Freed, Adv. Chem. Phys. **103**, 335 (1998).
- [22] G. Adam and J. H. Gibbs, J. Chem. Phys. **43**, 139 (1965).
- [23] The LCT free energy contains a term $\ln(d)$ [21], which complicates the discussion of the $d \rightarrow \infty$ limit. By $d \rightarrow \infty$, we mean an arbitrarily large but finite d .
- [24] The GET defines T_g by $\tau_\alpha(T_g) = 100$ s, and the isobaric fragility parameter follows as $m_P = \partial \log(\tau_\alpha) / \partial (T_g/T) |_{P, T=T_g}$. Using the parameters in the present work leads to $T_g = 313.5$ K and $m_P = 148.5$ in $d = 3$.
- [25] J. Dudowicz, J. F. Douglas, and K. F. Freed, J. Chem. Phys. **141**, 234903 (2014).
- [26] J. H. Gibbs and E. A. DiMarzio, J. Chem. Phys. **28**, 373 (1958).
- [27] See Supplemental Material at [URL will be inserted by publisher] for the derivation of the residual configurational entropy density, the dimensional dependence of the activation free energy ratio, and the results of the dimensionless isothermal compressibility and thermal expansion coefficient.
- [28] G. P. Johari, J. Chem. Phys. **132**, 124509 (2010).
- [29] T. A. Weber, G. H. Fredrickson, and F. H. Stillinger, Phys. Rev. B **34**, 7641 (1986).
- [30] T. A. Weber and F. H. Stillinger, Phys. Rev. B **36**, 7043 (1987).
- [31] H. G. E. Hentschel, S. Karmakar, I. Procaccia, and J. Zylberg, Phys. Rev. E **85**, 061501 (2012).
- [32] J. F. Kincaid, H. Eyring, and A. E. Stearn, Chem. Rev. **28**, 301 (1941).
- [33] T_l corresponds to a large τ_r since τ_r at T_c is already large for high d . We have confirmed that the general trend of the fitted K_{VFT} and T_{VFT} with d is unaffected by the reasonable choice of T_l .
- [34] Unfortunately, K_{VFT} is estimated in simulations using data above T_c [7], while K_{VFT} is obtained in our model from data below T_c . Moreover, simulations [7] and our calculations are performed at constant density and constant pressure, respectively. Hence, it is difficult to directly compare K_{VFT} in our model and simulations.
- [35] S. Sengupta, F. Vasconcelos, F. Affouard, and S. Sastry, J. Chem. Phys. **135**, 194503 (2011).
- [36] W.-S. Xu and K. F. Freed, J. Chem. Phys. **141**, 044909 (2014).
- [37] E. B. Stukalin, J. F. Douglas, and K. F. Freed, J. Chem. Phys. **131**, 114905 (2009).

Supplemental Material for Polymer Glass-Formation in Variable Dimension

S1. MEAN-FIELD ESTIMATION OF THE CONFIGURATIONAL ENTROPY AT LOW TEMPERATURES AND DEPENDENCE OF THE CRITICAL DIMENSIONALITY ON MOLAR MASS

The residual configurational entropy density $s_{c,r}$ [i.e., the low temperature (T) constant of the configurational entropy density s_c] can be obtained by analyzing the thermodynamics of the system in the limit where all lattice sites are occupied by chain segments. Hence, we focus on the low T regime of glass-formation where the polymer filling fraction φ (defined as the ratio of the total number of chain segments to the total number of lattice sites [21, 36]) approaches unity in order to estimate how the critical dimensionality, above which s_c ceases to vanish, depends on molecular parameters. For low T (e.g., $T = 10$ K), the factor $\exp(-\beta E_b)$ [where $\beta = 1/(k_B T)$ and E_b is the bending energy] in the LCT free energy nearly vanishes for large E_b [e.g., the present work uses $E_b = 800$ K, leading to $\exp(-\beta E_b) = \exp(-80)$ at $T = 10$ K]. In this limit, all terms multiplied by $\exp(-\beta E_b)$ in the LCT free energy disappear, and then taking $\varphi = 1$ leads to the greatly simplified expression for the free energy,

$$\beta f_r = \frac{1}{M} \ln \left(\frac{2}{z^L M} \right) + \left(1 - \frac{1}{M} \right) - \sum_{i=1}^6 C_i, \quad (\text{S1})$$

where M is the molar mass (defined as the total number of chain segments in a single chain), L designates the number of sub-chains in a single chain [21, 36], and C_i has the following form [36]:

$$C_i = C_{i,0} + C_{i,\epsilon}(\beta\epsilon) + C_{i,\epsilon^2}(\beta\epsilon)^2, \quad (\text{S2})$$

where ϵ is the nearest-neighbor van der Waals interaction energy. However, $C_{i,0}$, $C_{i,\epsilon}$, and C_{i,ϵ^2} are now independent of T , and, hence,

$$\beta \frac{\partial C_i}{\partial \beta} = C_{i,\epsilon}(\beta\epsilon) + 2C_{i,\epsilon^2}(\beta\epsilon)^2. \quad (\text{S3})$$

Consequently, the residual configurational entropy density, $s_{c,r} = -\partial f_r / \partial T|_{\varphi}$, emerges as

$$\begin{aligned} \frac{s_{c,r}}{k_B} = & -\frac{1}{M} \ln \left(\frac{2}{z^L M} \right) - \left(1 - \frac{1}{M} \right) \\ & + \sum_{i=1}^6 \left(C_i - \beta \frac{\partial C_i}{\partial \beta} \right). \end{aligned} \quad (\text{S4})$$

Substituting Eq. (S3) into Eq. (S4) leads to the relation,

$$\begin{aligned} \frac{s_{c,r}}{k_B} = & -\frac{1}{M} \ln \left(\frac{2}{z^L M} \right) - \left(1 - \frac{1}{M} \right) \\ & + \sum_{i=1}^6 [C_{i,0} - C_{i,\epsilon^2}(\beta\epsilon)^2]. \end{aligned} \quad (\text{S5})$$

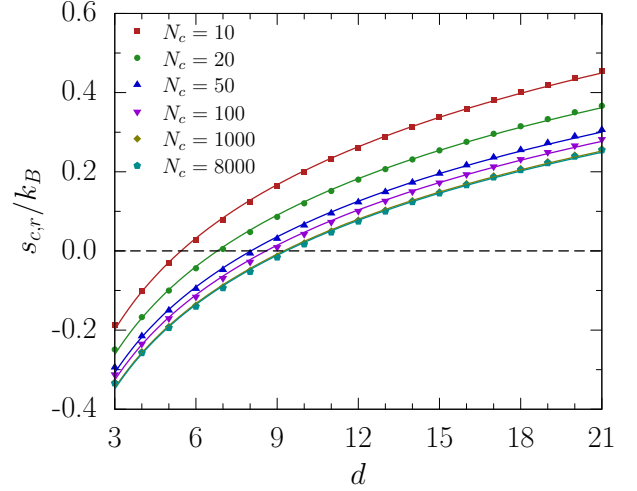


FIG. S1. Residual configurational entropy density $s_{c,r}/k_B$ as a function of d for various polymerization indices N_c for a melt of PP chains. The solid lines are fits to the equation $s_r/k_B = A \ln(d/2) + B$ with A and B being the fitting parameters. The critical dimensionality d_c , where $s_{c,r}$ starts to be positive, increases with N_c and saturates at $d = 10$ for sufficiently large N_c .

Taking advantage of the fact that $\sum_{i=1}^6 C_{i,\epsilon^2} = 0$ [36], $s_{c,r}$ finally appears in the simple form:

$$\frac{s_{c,r}}{k_B} = -\frac{1}{M} \ln \left(\frac{2}{z^L M} \right) - \left(1 - \frac{1}{M} \right) + \sum_{i=1}^6 C_{i,0}. \quad (\text{S6})$$

Since $C_{i,0}$ is now a function of d ($z = 2d$) and a set of geometrical indices that are determined from the monomer structure and molar mass M , $s_{c,r}$ is independent of T , ϵ , and E_b . Figure S1 displays the d dependence of $s_{c,r}$ for various polymerization indices N_c for a melt of PP chains. The “critical dimensionality” d_c , where $s_{c,r}$ starts to be positive, is found to increase with N_c , saturating at $d = 10$ for large N_c . The d dependence of $s_{c,r}/k_B$ in each case can be well described by the equation,

$$s_{c,r}/k_B = A \ln(d/2) + B, \quad (\text{S7})$$

where A and B are the fitting parameters. Figure S1 illustrates this variation. The filling fraction at the point at which s_c formally vanishes is somewhat less than unity, but this simple analytic argument is sufficient for estimating the N_c dependence of the critical dimensionality above which s_c no longer vanishes at low T .

S2. DIMENSIONAL DEPENDENCE OF THE RATIO OF THE ACTIVATION FREE ENERGIES IN THE HIGH AND LOW TEMPERATURE ARRHENIUS REGIMES

As discussed in the main text, the ratio $s_c^*/s_{c,r}$ defines the relative magnitude of the activation free energy

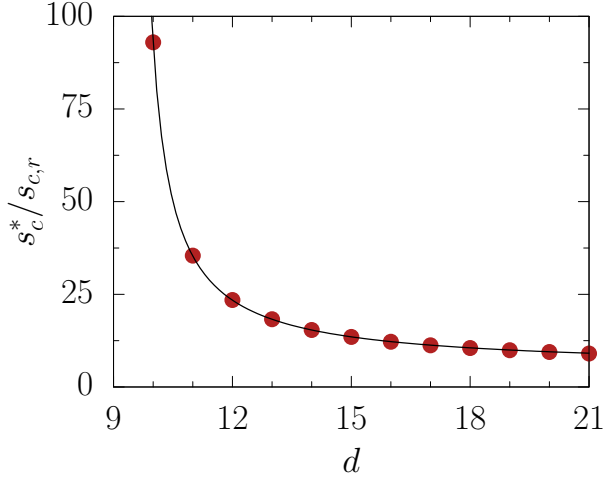


FIG. S2. Activation free energy ratio $s_c^*/s_{c,r}$ as a function of d for $d \geq d_c$. The line is a fit to the equation $s_c^*/s_{c,r} = 1/[A - B/\ln(d/2)]$ with the fitted constants, $A = 0.325$ and $B = 0.505$.

for relaxation in the high and low T Arrhenius regimes above d_c that we separately characterize as being simple fluid-like and glass-like because of the large difference of relaxation times in these different regimes of T . The GET allows us to calculate this activation free energy ratio as a function of d , and we illustrate our findings in Fig. S2. Curiously, the activation free energy ratio falls with increasing d , indicating that the dynamics of the high and low T regimes actually becomes similar in high d , where the activation free energy ratio saturates at a minimal value of about 3. The d variation of the activation free energy ratio is well represented by the approximant:

$$s_c^*/s_{c,r} = 1/[A - B/\ln(d/2)], \quad d > d_c, \quad (\text{S8})$$

where the fitting parameters are estimated to be $A = 0.325$ and $B = 0.505$. Because the activation free energy in the high T regime is large for high d , increasing this quantity by a factor of 3 in high d translates into an extremely large increase in relaxation times in the low T Arrhenius regime.

S3. DIMENSIONAL DEPENDENCE OF THE REDUCED ISOTHERMAL COMPRESSIBILITY AND THERMAL EXPANSION COEFFICIENT

Materials that pack more efficiently can be expected to have a lower and more weakly T dependent isothermal compressibility (κ_T) or thermal expansion coefficient (α_P), while those exhibiting a high degree of packing frustration due to the complexity of the molecular structure should exhibit a relatively large and relatively strongly T dependent κ_T or α_P . Previous analyses [37] of GET calculations in $d = 3$ reveal the existence of a very strong correlation between the filling fraction at T_g and the fragility when the molar mass, cohesive interaction, or

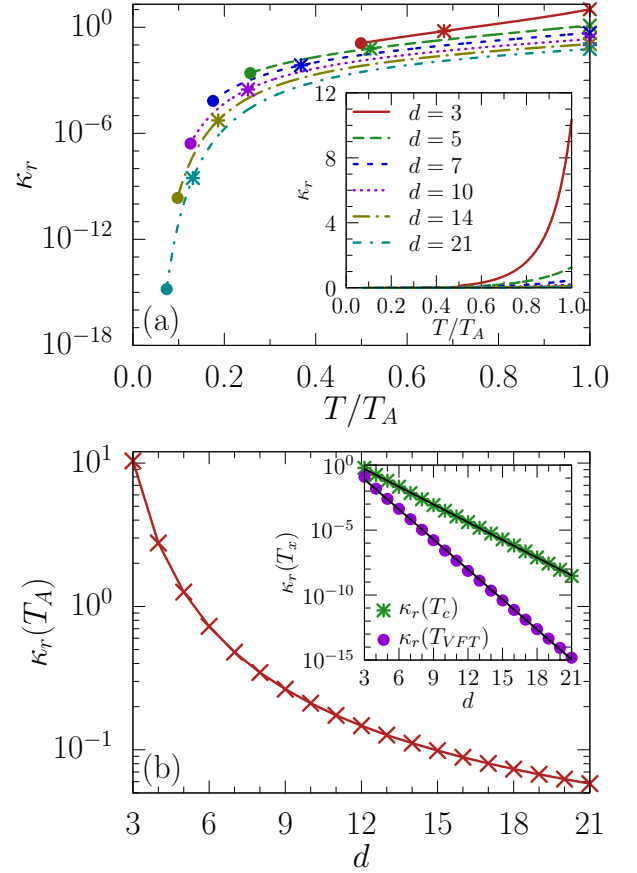


FIG. S3. (a) Main: Reduced isothermal compressibility $\kappa_r = \kappa_T(k_B T)/\rho$ as a function of T/T_A for various d . Crosses, asterisks, and circles indicate the points corresponding to T_A , T_c , and T_{VFT} , respectively. Data are presented in the T range (T_{VFT} , T_A) of interest in the present work. Inset: Same plot but shown in a linear scale representation. (b) Main: $\kappa_r(T_A)$ as a function of d . Inset: $\kappa_r(T_c)$ and $\kappa_r(T_{VFT})$ as a function of d . Lines in the set indicate the exponential fits, $\kappa_r(T_x) = A_x \exp(-B_x d)$ ($x = c$ or VFT) with A_x and B_x the fitting parameters. We obtained the fitting estimates: $A_c = 11.7$ and $B_c = 1.05$ and $A_{VFT} = 16.3$ and $B_{VFT} = 1.77$.

pressure is varied. Moreover, molecules in fragile polymer fluids are predicted to pack less efficiently in the glassy state than those in stronger glass-forming polymer fluids. These observations deduced from the GET calculations indicate that packing efficiency is a central factor for understanding the fragility of glass-formation. This line of reasoning naturally leads to the expectation that κ_T and α_P correlate strongly with the fragility.

Because our extensive analyses in $d = 3$ reveal that the dimensionless isothermal compressibility, $\kappa_r = \kappa_T(k_B T)/\rho$ with $\rho = \varphi V_{\text{cell}}$, and the dimensionless thermal expansion coefficient, $\alpha_r = T\alpha_P$, strongly correlate with the fragility of glass-formation, we consider these reduced quantities in d dimensions. Figures S3 and S4 indicate the GET model predictions for κ_r and α_r as a function of T/T_A for various d . Evidently, the strength

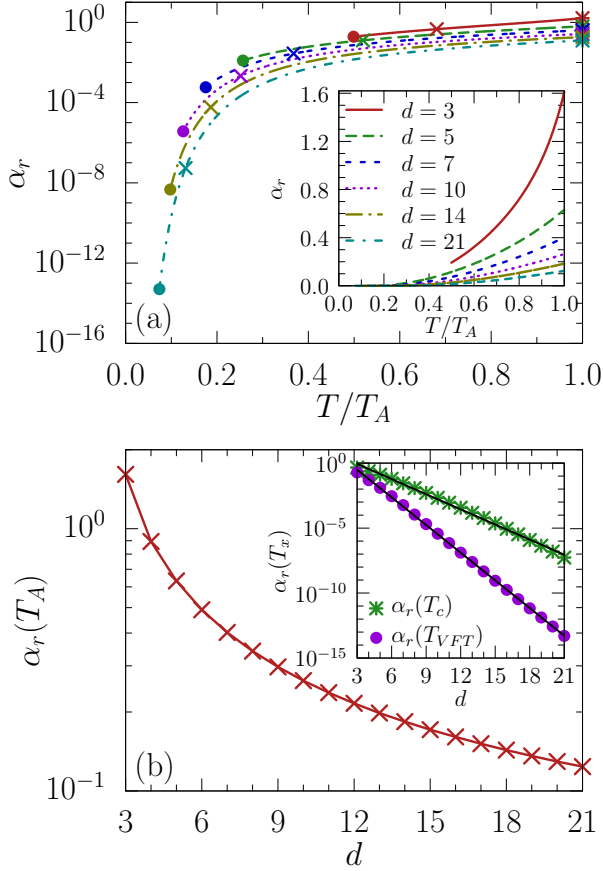


FIG. S4. (a) Main: Reduced thermal expansion coefficient $\alpha_r = T\alpha_P$ as a function of T/T_A for various d . Crosses, asterisks, and circles indicate the points corresponding to T_A , T_c , and T_{VFT} , respectively. Data are presented in the T range (T_{VFT} , T_A) of interest in the present work. Inset: Same plot but shown in a linear scale representation. (b) Main: $\alpha_r(T_A)$ as a function of d . Inset: $\alpha_r(T_c)$ and $\alpha_r(T_{VFT})$ as a function of d . Lines in the set indicate exponential fits: $\alpha_r(T_x) = A_x \exp(-B_x d)$ ($x = c$ or VFT) with A_x and B_x the fitting parameters. We obtained the fitting estimates: $A_c = 12.7$ and $B_c = 0.89$ and $A_{VFT} = 42.1$ and $B_{VFT} = 1.63$.

of the T dependence of both κ_r and α_r weakens with increasing d , and both κ_r and α_r progressively decreases with d for fixed reduced temperatures T/T_A . The insets to Figs. S3 and S4 indicate that $\kappa_r(T_x)$ ($x = c$ or VFT) and $\alpha_r(T_x)$ ($x = c$ or VFT) decay exponentially with d to a high approximation. The slower variation with T of κ_r and α_r and the overall values of κ_r and α_r all reflect decreased packing frustration with increasing d , thereby confirming the qualitative *geometrical* origin of the reduced fragility found upon increasing d . Both the reduced fragility with increasing d and the corresponding return to Arrhenius relaxation are consequences of the reduction of packing frustration in high d where space is more “open” and packing constraints are more weakly “felt”.